


CVD ZnSe (CVD Zinc Selenide) - Main Properties

Zinc selenide is a clear yellow polycrystalline material with a grain size of approximately 70µm, transmitting in the range 0.5-15µm. It is essentially free of extrinsic impurity absorptions, providing extremely low bulk losses from scatter. Zinc Selenide, produced by the method of chemical vapour deposition, is the preferred material for optics used in high power CO₂ laser systems due to its low absorption at 10.6µm. However it is also a popular choice in systems operating at various bands within its wide transmission range. ZnSe has a high resistance to thermal shock making it the best material for high power CO₂ laser systems. ZnSe however is only 2/3 the hardness of ZnS multi-spectral grade but the harder anti-reflectance coatings do serve to protect ZnSe. Zinc Selenide is a relatively soft material and scratches rather easily. It requires an anti-reflection coating due to its high refractive index if high transmission is required. ZnSe has a rather low dispersion across its useful transmission range. For high power applications, it is critical that the material bulk absorption and internal defect structure be carefully controlled, that minimum-damage polishing technology be employed, and the highest quality optical thin film coatings are used.

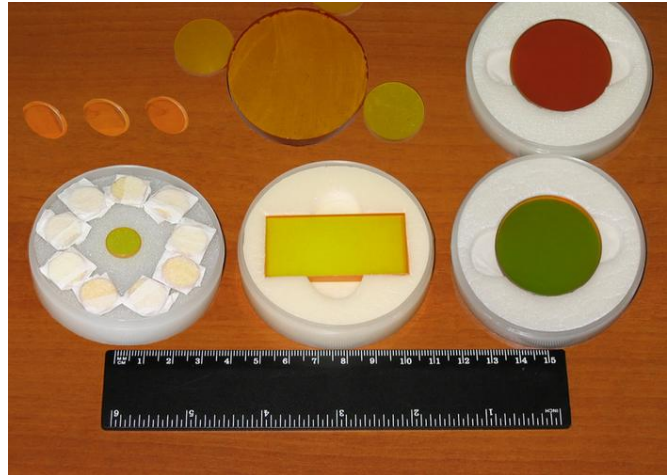

Optical Properties

Bulk Absorption Coefficient @ 10.6µm 0.0005/cm
 Temp. Change of Refractive Index @ 10.6µm 61x10⁻⁶/°C
 Refractive Index Non-homogeneity @ 632.8nm <6X10⁻⁶

Thermal Properties

Thermal Conductivity 0.18W/cm/°C
 Specific Heat 0.356J/g/°C
 Linear Expansion Coefficient @ 20°C 7.57x10⁻⁶/°C



Mechanical Properties

Young's Modulus 6.85X10¹¹ dyne/cm²
 Rupture Modulus 5.7X10⁸ dyne/cm²
 Knoop Hardness 110-130Kg/mm²
 Density 5.27g/cm³
 Poisson's Ratio 0.28

Refractive Index of CVD ZnSe:

Wavelength (µm)	Index	Wavelength (µm)	Index	Wavelength (µm)	Index	Wavelength (µm)	Index
0,54	2,68	1,8	2,45	7,4	2,42	13,0	2,39
0,58	2,63	2,2	2,44	7,8	2,42	13,4	2,38
0,62	2,60	2,6	2,44	8,2	2,42	13,8	2,38
0,66	2,58	3,0	2,44	8,6	2,41	14,2	2,37
0,70	2,56	3,4	2,44	9,0	2,41	14,6	2,37
0,74	2,54	3,8	2,43	9,40	2,41	15,0	2,37
0,78	2,53	4,2	2,43	9,80	2,41	15,4	2,36
0,82	2,52	4,6	2,43	10,2	2,41	15,8	2,36
0,86	2,51	5,0	2,43	10,6	2,40	16,2	2,35
0,90	2,50	5,4	2,43	11,0	2,40	16,6	2,35

0,94	2,50	5,8	2,43	11,4	2,40	17,0	2,34
0,98	2,49	6,2	2,43	11,8	2,39	17,4	2,34
1.0	2,49	6,6	2,42	12,2	2,39	17,8	2,33
1,4	2,46	7.0	2,42	12,6	2,39	18,2	2,33

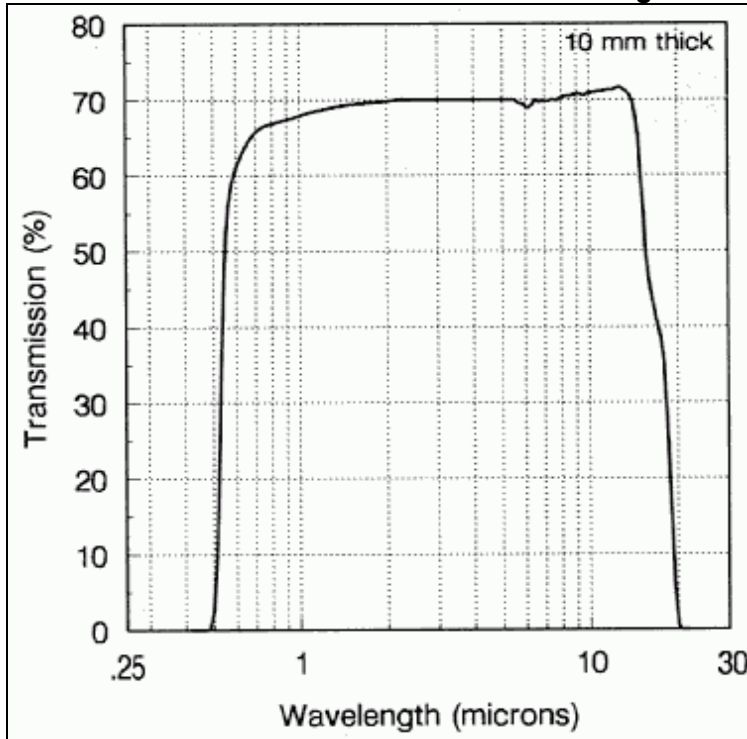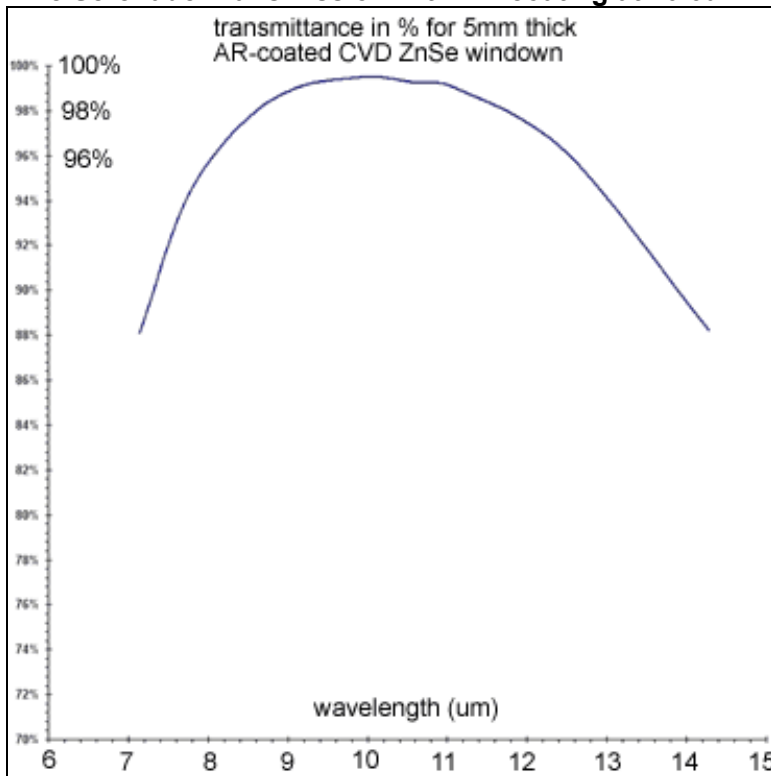Zinc Serenade Transmission without AR-coating

Zinc Serenade Transmission with AR-coating at 10.6um


Adhesive-Free Bond (AFB[®]) Components

We are the world leader in the manufacture of finished composite crystal and glass components for solid-state lasers. We patented its Adhesive-Free Bond[®] technology, which enables the joining of crystal or glass optical materials without the use of an adhesive or an organic or inorganic bonding aid. Composite optical components manufactured using Adhesive-Free Bond (AFB[®]) technology will enable cost-effective systems of increased output power and improved beam quality.

AFB[®] allows for the separation of functionalities of laser components into lasing and non-lasing regions, which is critical for high power DPSSL systems. Our AFB[®] composites offer a new degree of freedom for the design engineer's realization of rugged, compact, solid state laser systems.

In addition to providing AFB[®], we possess full-finishing capabilities. We work to support our customers from the conceptual design phase all the way through to large-scale production. Please contact us to discover how AFB[®] composites can improve your laser system.



1. Standard Adhesive-Free Bond (AFB[®]) Components

Slab, Disk, Rod AFB[®] Components

We have product lines of various Slabs, Disks and Rod-based AFB[®] components.

Vanadate AFB[®] Components

AFB[®] YVO4 or GdVO4 components are extremely useful for higher power in YVO4-based laser systems. Undoped end-caps increase damage threshold by separating the pump input face with the lasing doped portion. We produce slabs and rods with plano or spherical end faces.

Microchip AFB[®] Components

AFB[®] microchips, especially in the form of Nd:YAG/Cr4+:YAG passively Q-switched microchips have found a host of applications due to their compact size and the incorporation of both the lasing material and q-switch into a monolithic element. This approach minimizes system complexity and system size, and maximizes efficiency.

Waveguide AFB[®] Components

Tolerances of $\lambda/30$ flatness over the core and dimensional tolerances down to +/- 0.001mm over the core are available.

2. Customized AFB[®] Components

We welcome all inquiries about the feasibility of AFB[®] composite optical components. We are interested in discussing and manufacturing new material combinations and structural geometries. It is our goal to provide high-quality composites that will provide a solution for your system's needs, so we encourage any design submissions for review.

Large AFB[®] Components

We have become well known for its ability to produce crystals of larger sizes than previously possible.

MOSAIC AFB[®] Laser Components

With MOSAIC AFB[®] multiple crystals are edge-AFB[®]d together in array fashion to produce larger plates or slabs. For example, if the maximum size of a certain crystal is 50x50x5mm, four plates could

be MOSAIC AFB[®]d to produce one 100x100x5mm plate. This is useful for both active laser crystals such as Yb:YAG, Nd:YAG, Nd:GGG, Yb:S-FAP and inactive window material such as sapphire or spinel.

3. Adhesive-Free Bond (AFB[®]) Technology

Adhesive-Free Bonding (AFB[®]) is patented technology developed and owned by us. Since laser environments dictate robust components with minimal loss or damage, Adhesive-Free Bond (AFB[®]) has been developed to produce strong and optically transparent bonds. Both similar and dissimilar crystals and glasses may be bonded using this unique process. In most cases AFB[®] is as strong as bulk material.

We have patents in the U.S. for bonding without any adhesive at the interface. We had originally called the process diffusion bonding because volatile components are diffusing out during the bonding process. Thermal and optical bonding are two other names for the same type of bond. Chemically activated bonds have some chemical component at the interface between components and are therefore not as strong or as stable as if there were no adhesive at the interface. Chemically activated bonds also are not compatible with composites consisting of differing materials such as YAG and sapphire or YAG and spinel, whereas adhesive-free bonds are.

4. Adhesive-Free Bonding Applications:

Defense and Aerospace

- Missile defense
- Lidar
- Remote Sensing
- Range-Finding
- Countermeasures
- Wind speed measurement
- Cloud and aerosol monitoring

Materials Processing

- Drilling, cutting, welding
- Marking
- Stereolithography
- Thickness of thin films

Medical Surgery

- Ophthalmology
- Orthopedics
- Microsurgery
- Aesthetic skin resurfacing
- Hair removal

OEM

- High Power DPSSL
- OPO Pump
- Ring laser
- Microchip laser
- CD writing



5. Adhesive-Free Bond (AFB[®]) Features

- Elimination of ground state absorption losses of quasi-3-level lasing ions, especially for high power Yb:YAG based rod and slab systems
- Reduction of parasitic oscillations by using Adhesive-Free Bond (AFB[®]) undoped or laser radiation absorbing crystals
- Reduction of thermal lensing and other thermal effects with undoped YAG or sapphire acting as heat sink
- Passive q-switching with e.g. Cr⁴⁺:YAG as integral component of lasing element
- Elimination of spatial hole burning for non-planar ring laser (NPRO) by allowing the reflected beam to traverse through an undoped crystal

- Mechanical support of thin lasing layers, down to about 2-4 μ thickness, thereby also essentially eliminating thermal effects in this geometry to a negligible level
- Undoped ends in rods, shaped as straight cylinders or flanges, can function as light ducts for pump radiation
- Light guiding and wave guiding effects by combining dissimilar compatible materials of different refractive index, e.g. YAG lasing medium with sapphire cladding, YAG with spinel, and GGG with YAG cladding

6. Material Combinations

Materials that can be Adhesive-Free Bonded (AFB[®]) include common laser host media such as oxides (YAG, GGG, Sapphire, Spinel), fluorides (YLF, LuLiF, S-FAP), vanadates (YVO₄, GdVO₄), crystals as well as glasses. In selected compatible cases (for example YAG/Spinel, YAG/Sapphire and YAG/Glass), dissimilar materials may be AFB[®]d with high bond strength. The most common combinations are YVO₄/Nd:YVO₄, Yb:YAG/YAG, Yb:YAG/sapphire, Cr⁴⁺:YAG/Nd:YAG, Nd:YAG/YAG, Nd:YAG/Cr⁴⁺:YAG.

AFB[®] composites are available with the following materials, and we welcome inquiries regarding the feasibility of any materials that you do not see listed:

- YAG
- LuAG
- GGG
- TeO₂
- SiC
- Diamond
- Sapphire
- LiNbO₃
- YALO (YAP)
- YVO₄
- YLF
- LuLiF
- S-FAP
- Ti:Sapphire
- SrTiO₃
- Spinel
- Laser glass
- Fused silica
- Optical glass
- Ceramics
- KTP
- ZGP
- ALON
- GVO₄



Optical coatings at bonded interfaces are available.

7. Pump Geometries

Adhesive-Free Bond (AFB[®]) is useful for end-, face-, and side-pumped laser geometries to greatly reduce thermal end-effects and to provide a new degree of engineering freedom for the laser designer. End- and face-pumped systems benefit greatly from AFB[®] undoped end caps due to the higher damage threshold of the pump end of the laser component and separating the pump absorption from the optical coating. Side-pumped geometries also benefit from higher damage thresholds with AFB[®] of undoped end caps and high thermal conductivity side claddings.

8. Properties of Composites

Although there are differences between composites, the following summary of properties applies to most representative combinations:

Mechanical and Thermal

- Flexural strength: Same as non-composite control samples
- Thermal shock resistance: Same as non-composite controls; no separation at interface during failure
- Can be finished and optically coated like conventional crystals


Optical Properties

- Transmitted wave front unchanged; may actually be improved in long rods by selective arrangement of individual components with respect to each other
- Negligible stress birefringence

Interface Properties


- Very high laser damage resistance
- Negligible scatter or absorptive loss
- Fresnel reflection corresponding to difference in refractive index of components

Typical AFB Rods

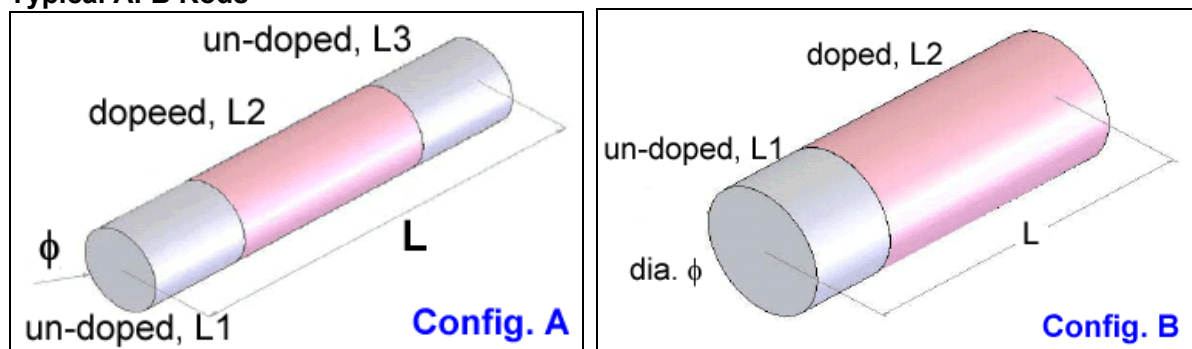

P/N	Con fig	ϕ	L	Un-doped		doped		Un-doped		End surface	Coating	Qty
				M.	L1	M & %	L2	M.	L3			
0128	A	4	20	YAG	5	Nd:YAG, 1.1	10	YAG	5	F/F	none	
0136	A	5	22	YAG	5	Nd:YAG, 1.0	12	YAG	5	1° wedge	none	2
0138	A	6.35	156	YAG	20	Nd:YAG, 0.6	116	YAG	20	F/F	none	1
0143	A	2	8.5	YAG	2.75	Nd:YAG, 1.0	3	YAG	2.75	F/F	none	S
0150	A	2.7	55	YAG	9.5	Nd:YAG, 1.1	36	YAG	9.5	F/F	none	1
0153	A	3	63	YAG	7	Nd:YAG, 0.8	49	YAG	7	F/F	none	1
0156	A	2	10	YAG	2.5	Nd:YAG, 0.6	5	YAG	2.5	F/F	none	4
0165	A	4	54	YAG	7	Nd:YAG, 0.1	40	YAG	7	F/F	none	2
0172	A	3	3	YAG	1	Nd:YAG, 1.1	1	YAG	1	F/F	none	1
0173	A	4	20	YAG	5	Nd:YAG, 1.1	10	YAG	5	F/F	none	1
0174	A	3	4	YAG	1	Nd:YAG, 1.1	2	YAG	1	F/F	none	2
0180	A	6.35	140	YAG	20	Nd:YAG, 0.6	100	YAG	20	F/F	none	1
0184	A	3	54	YAG	7	Nd:YAG, 0.1	40	YAG	7	F/F	none	1
0185	A	2	8.5	YAG	2.75	Nd:YAG, 1.0	3	YAG	2.75	F/F	none	2
0199	A	3	54	YAG	7	Nd:YAG, 0.1	40	YAG	7	F/F	none	4
0140	A	1.5	65	YAG	22.5	Nd:YAG, 0.5	20	YAG	22.5	F/F	none	1
0192	A	4	20	YAG	5	Nd:YAG, 1.1	10	YAG	5	F/F	Note 1)	1
0200	A	3	54	YAG	7	Nd:YAG, 0.1	40	YAG	7	F/F	none	2
0134	A	3	95	YAG	15	Tm:YAG, 3.0	65	YAG	15	F/F	none	1
0155	A	3	105	YAG	20	Tm:YAG, 3.0	65	YAG	20	F/F	none	1
0162	A	4	20	YAG	5	Tm:YAG, 3.0	10	YAG	5	F/F	none	1
0186	A	2.5	27.8	YAG	5	Tm:YAG, 3.0	17.8	YAG	5	F/F	none	1
0202	A	3	85	YAG	10	Tm:YAG, 3.0	65	YAG	10	F/F	none	1
0210	A	3	100	YAG	10	Er:YAG, 0.5	80	YAG	10	F/F	none	1
0203	A	2	50	YAG	15	Yb:YAG, 3.0	20	YAG	15	F/F	none	1
0182	A	4	52	YLF	16	Th:YLF	20	YLF	16	F/F	none	1
0500	A	8	150	YAG	5	Nd:YAG, 1.1	140	YAG	5	F/F	none	
0195	B	12.7	12.7	YAG	6.35	Sapphire	6.36			F/F	none	1
0167	B	5	15	YAG	4	Nd:YAG, 1.0	11			F/F	none	2
0191	B	9	12	YAG	3	Nd:YAG, 0.9	9			F/F	none	1
0145	B	2.5	11	YAG	3	Nd:YAG, 1.1	8			F/F	none	2
0141	B	3	8	YAG	2	Nd:YAG, 1.1	6			F/F	none	S
0163	B	3	10	Sapphire	8	Nd:YAG, 1.1	2			F/F	none	1

Note: 1)HR 1064nm, HT 808nm

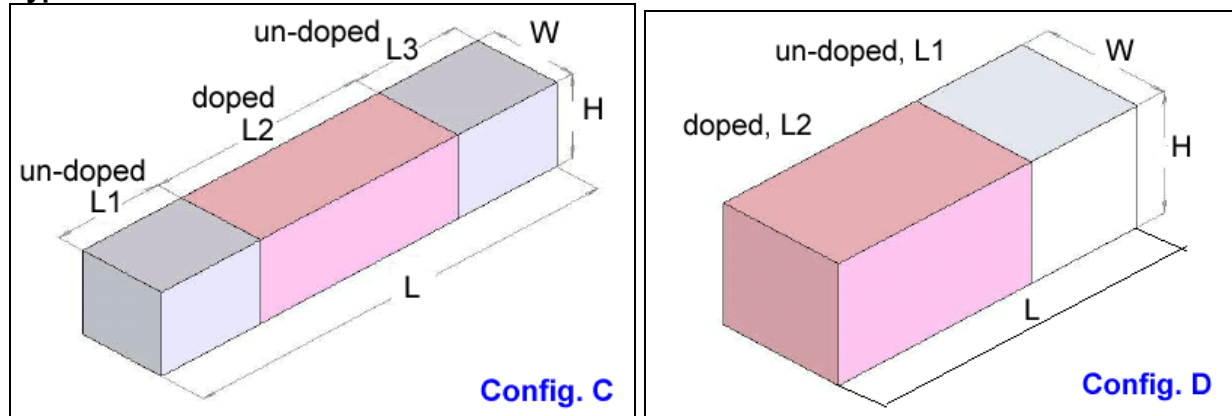Typical AFB Slabs


P/N	Con fig.	W	H	L	Un-doped		doped		Un-doped		End surface	Coating	Qty
					M.	L1	M. & %	L2	M.	L3			
0132	C	4	4	20	YAG	5	Nd:YAG, 1.1	10	YAG	5	F/F	Note 1)	2
0139	C	5	5	10	YAG	1	Nd:YAG, 1.0	8	YAG	1	F/F	none	1
0151	C	12	2	6	YAG	2	Nd:YAG, 0.6	2	YAG	2	F/F	none	3
0179	C	9	3	64	YAG	2	Nd:YAG, 1.3	60	YAG	2	F/F	none	2
0142	C	2.5	2	17.4	YAG	3.3	Yb:YAG, 1.5	10.8	YAG	3.3	F/F	none	1
0147	C	4	2	28	YAG	12	Yb:YAG, 15	4	YAG	12	F/F	none	1
0161	C	3	3	3.5	YAG	1	Yb:YAG, 15	1.5	YAG	1	F/F	none	3
0164	C	6	3	3.5	YAG	1	Yb:YAG, 15	1.5	YAG	1	F/F	none	1
0170	C	3	3	2.5	YAG	0.5	Yb:YAG, 10	1.5	YAG	0.5	F/F	none	1
0187	C	50	4	6.5	YAG	3	Yb:YAG, 0.5	0.5	YAG	3	F/F	Note 2)	1
0197	C	3	3	20	YVO4	2.5	Nd:YVO4, 0.3	15	YVO4	2.5	F/F	none	2
0133	C	3	3	7.5	YVO4	3	Nd:YVO4, 1.0	1.5	YVO4	3	F/F	none	2
0135	C	3	3	7	YVO4	3	Nd:YVO4, 0.3	1	YVO4	3	F/F	none	2
0137	C	3	3	7	YVO4	3	Nd:YVO4, 0.3	1	YVO4	3	F/F	none	1
0144	C	2.5	2.5	14	YVO4	3.4	Nd:YVO4, 0.3	8	YVO4	2.6	F/F	none	1
0152	C	4	4	14	YVO4	3	Nd:YVO4, 0.3	8	YVO4	3	F/F	none	1
0212	C	4	4	20	YVO4	2.5	Nd:YVO4, 0.3	15	YVO4	2.5	F/F	none	
0171	C	3	3	10.5	YVO4	5	Nd:YVO4, 1.0	0.5	YVO4	5	F/F	none	1
0183	C	14	3	3	YVO4	1.25	Nd:YVO4, 0.3	0.5	YVO4	1.25	F/F	none	2
0166	C	4	4	22	YLF	5	Tm:YLF, 3.5	12	YLF	5	F/F	none	1
0126	C	4	4	12	YLF	5	Tm:YLF, 3.5	8	YLF	2	F/F	none	1
0211	C	3	3	25	YVO4	3	Nd:YVO4, 0.3	19	YVO4	4	F/F	none	
127A	D	4	4	10.4	YVO4	3.7	Nd:YVO4, 0.5	6.7			F/F	none	1
127B	D	4	4	10.6	YVO4	3.8	Nd:YVO4, 0.5	6.8			F/F	none	1
127C	D	4	4	10.3	YVO4	3.5	Nd:YVO4, 0.5	6.8			F/F	none	3
0130	D	3	3	10	YVO4	2	Nd:YVO4, 0.3	8			F/F	none	
0131	D	3	3	10	YVO4	2	Nd:YVO4, 0.3	8			F/F	Note 1)	
0148	D	3	3	10	YVO4	2	Nd:YVO4, 0.5	8			F/F	Note 3)	1
0157	D	4	4	8.1	YVO4	0.3	Nd:YVO4, 2.0	7.8			F/F	none	1
0158	D	14	3	3.3	YVO4	3.0	Nd:YVO4, 1.0	0.3			F/F	none	1
0159	D	3.25	3	6.5	YVO4	3.25	Nd:YVO4, 1.0	3.25			F/F	none	1
0160	D	2.8	2.8	11.6	YVO4	3.4	Nd:YVO4, 1.0	8.2			F/F	none	1
0168	D	3	3	7.9	YVO4	3.4	Nd:YVO4, 0.5	4.5			F/F	none	1
0188	D	3.5	3	6.5	YVO4	3.0	Nd:YVO4, 0.5	3.5			F/F	none	3

Note: 1) AR@1064nm & 808nm

2) AR@1030nm & 940nm

3) S1:R<0.1%@1064; S2: R<0.1% @1064, R<3% @808nm


Nd:YAG Rods

Capabilities:

- Rod size: 2 - 12mm in diameter and 1 - 180mm in length;
- Nd dopant concentration : 0.6% - 1.3%;
- Polishing;
- AR-coating or/and dichroic coating;

Specifications:

- | | |
|---------------------------------|------------------------------|
| • Material: | Nd:YAG |
| • Nd dopant concentration: | as specified $\pm 0.1\%$ |
| • Parallelism: | $\leq 10''$ |
| • Flatness: | $\lambda/10 @ 632\text{nm}$ |
| • Perpendicularity: | $< 2'$ |
| • Interference fringes: | $< 0.5 \text{ fringes/inch}$ |
| • Extinction ratio: | $> 15\text{db}$ |
| • Transmission with AR coating: | $\geq 99.8\%$ |
| • Damage threshold: | $> 15\text{J/cm}^2$ |

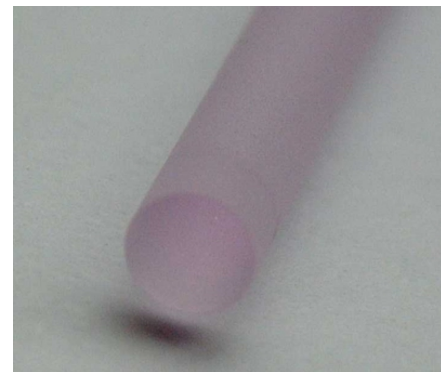

Nd:YAG Crystal

During the last decade, Nd:YVO₄ has been developed as a promising substitutes for Nd:YAG in diode-pumped lasers due to its high absorption and emission cross-sections. However, the applications of Nd:YVO₄ are limited due to its poor physical-mechanical properties and growth difficulty etc. Now, we have developed the high-doped Nd:YAG (SUPER-Nd:YAG) recently. It shows high absorption cross-section and have many advantages over Nd:YVO₄:

- Due to the cubic symmetry and high quality, Nd:YAG is easy to operate with TEM₀₀ mode
- Nd:YAG can be Q-switched with Cr⁴⁺:YAG directly
- Nd:YAG can produce blue laser with the frequency-doubling of 946nm
- Nd:YAG can be operated in a very high power laser up to kW level

The high neodymium-ion doped YAG has been grown by the novel technique-Temperature Gradient Technique(TGT). The Nd concentration can be doped up to 3%. As large as $\phi 100 \times 80\text{mm}$ bulk crystals with excellent optical homogeneity, less scattering particles, low dislocation density have been obtained.

Basic Properties:

Chemical Formula:	Y ₃ Al ₅ O ₁₂
Crystal structure:	Cubic
Lattice constant:	12.01Angstrom
Melting point:	1970° C
Density:	4.5g/cm ³
Reflective Index:	1.82
Thermal Expansion Coefficient:	7.8x10 ⁻⁶ /K <111>
Thermal Conductivity (W/m/K):	14W/m/K, 20° C 10.5W/m/K, 100° C
Mohs hardness:	8.5
Stimulated Emission Cross Section:	2.8x10 ⁻¹⁹ cm ⁻²
Relaxation Time of Terminal Lasing Level:	30 ns
Radiative Lifetime:	550 μs
Spontaneous Fluorescence:	230 μs
Linewidth:	0.6 nm
Loss Coefficient:	0.003 cm ⁻¹ @ 1064nm

Laser Properties:

- SUPER-Nd:YAG shows high absorption coefficients at pumping wavelengths. Therefore, a crystal short-in length (e.g.1mm) is preferred and compact microchip lasers can be constructed by using SUPER-Nd:YAG.
- Due to the broader and smoothly-varied bandwidth of absorption, it allows of less stringent requirements of temperature control.
- Almost same output have been achieved both in a (111)-cut 1mm long Nd:YAG and an a-cut 1mm long YVO4 microchip lasers with a very short (9mm) laser cavity.

Spectra properties with concentration:

Nd:Dopant	2.5%	2%	1.5%	1.3%	1.1%	1%
Fluorescence lifetime	160 μ s	180 μ s	200 μ s	210 μ s	220 μ s	240 μ s
Absorption coefficient	7.55cm ⁻¹	6.57 cm ⁻¹	5.36 cm ⁻¹	4.66 cm ⁻¹	3.88 cm ⁻¹	3.55 cm ⁻¹

Nd:YAG Specifications:

Standard Dimensions:	3x3x3mm ³ , 3x3x1mm ³ (cubic)
Diameter:	φ3-12mm (rod)
Length:	1-152mm
Crystallographic orientation:	<111>
Nd Dopant Level:	0.7, 0.9, 1.0, 1.1, 1.3, 1.5, 2.0, 2.5± 0.1at%
Extinction Ratio:	>28 dB
Optical quality:	<0.5 fringes/inch
Diameter tolerance:	± 0.05mm
Length tolerance:	± 0.7mm
End face perpendicularity:	<5 arc minutes
Parallelism:	<10 arc seconds
Wavefront distortion:	$\lambda/8$
Flatness:	$\lambda/10$
Surface quality:	10/5 @MIL-O-13830A
HR-Coating:	R>99.8%@1064nm and R<5%@808nm
AR-Coating (Single layer MgF2):	R<0.25% per surface (@1064nm)

We can also provide Nd:YAG rod with multilayer hard coating that can be used for high power laser.

Nd:YVO4 Crystal

Nd:YVO4 is the most efficient laser crystal for diode-pumped solid-state lasers. Its good physical, optical and mechanical properties make Nd:YVO4 an excellent crystal for high power, stable and cost-effective diode-pumped solid-state lasers. Compared with Nd:YAG for diode laser pumping, Nd:YVO4 lasers possess:



- Lower lasing threshold and higher slope efficiency
- Large stimulated emission cross-section at lasing wavelength
- High absorption over a wide pumping wavelength bandwidth
- Low dependency on pumping wavelength and tend to single mode output
- Optically uniaxial and large birefringence emit strongly-polarized laser

We provide high quality and large size Nd:YVO4 and pure YVO4 crystal as large as $\phi 35 \times 50 \text{mm}^3$ bulk crystal and $\phi 20 \times 20 \text{mm}^3$ finished crystal at a very competitive price.

Basic Properties:

Atomic Density:	1.26×10^{20} atoms/cm ³ (Nd 1.0%)
Crystal Structure:	Zircon Tetragonal, space group D _{4h} -I4/amd a=b=7.1193 Angstrom, c=6.2892 Angstrom
Density:	4.22g/cm ³
Mohs Hardness:	4-5 (Glass-like)
Thermal Expansion Coefficient (300K):	$a_a = 4.43 \times 10^{-6}/\text{K}$; $a_c = 11.37 \times 10^{-6}/\text{K}$
Thermal Conductivity Coefficient (300K):	//C: 0.0523W/cm/K; \perp C: 0.0510W/cm/K

Optical Properties:

Lasing wavelength:	1064nm, 1342nm
Thermal optical coefficient (300K):	$dn_o/dT = 8.5 \times 10^{-6}/\text{K}$, $dn_e/dT = 2.9 \times 10^{-6}/\text{K}$
Stimulated emission cross-section:	$25 \times 10^{-19} \text{cm}^2$ @1064nm
Fluorescent lifetime:	90 μ s
Absorption coefficient:	31.4cm^{-1} @810nm
Intrinsic loss:	0.02cm^{-1} @1064nm
Gain bandwidth:	0.96nm @1064nm
Polarized laser emission:	π polarization; parallel to optic axis(c-axis)
Diode pumped optical to optical efficiency:	>60%

Laser Properties:

The Nd:YVO4 crystal has large stimulated emission cross-sections at both 1064nm and 1342nm. The stimulated emission cross-section of an a-axis cut Nd:YVO4 crystal at 1064nm is about 4 times higher than that of the Nd:YAG crystal. Although the lifetime of Nd:YVO4 is about 2.7 times shorter than that of Nd:YAG. Because of its high pump quantum efficiency, the slope efficiency of Nd:YVO4 can be very high if the laser cavity is properly designed.

Nd:YVO4 Specifications:

Transmitting wavefront distortion	less than $\lambda/4$ @ 633 nm
Dimension tolerance	(W \pm 0.1 mm) x (H \pm 0.1 mm) x (L + 0.2 mm/-0.1)
Clear aperture	>90% central area
Flatness	$\lambda/8$ @633nm, & $\lambda/4$ @633nm for thickness less than 2mm
Scratch/Dig code	10/5 to MIL-O-13830A
Parallelism	better than 20 arc seconds
Perpendicularity	5 arc minutes
Angle tolerance	$< \pm 0.5^\circ$
AR coating	R<0.2% at 1064nm, HR coating R>99.8% at 1064nm, T>95% at 808nm
Quality warranty period	one year under proper use.

Er:YAG

Erbium doped Yttrium Aluminum Garnet (Er:Y₃Al₅O₁₂ or Er:YAG) combine various output wavelength with the superior thermal and optical properties of YAG. It is an excellent laser crystal which lasers at 2.94μm. This wavelength is the most readily absorbed into water and hydroxylapatite of all existing wavelengths and is considered a highly surface cutting laser. It is a well known material for medical applications.

Material Properties of Er:YAG crystal

Chemical formula	Er ³⁺ :Y ₃ Al ₅ O ₁₂
Crystal structure	cubic
Melting point:	1970 °C
Density, g/cm ³	5,35
Mohs hardness	8.5
Thermal expansion coefficient	9,5 x 10-6 K-1 (a axis) 4,3 x 10-6 K-1 (b axis) 10,8 x 10-6 K-1 (c axis)
Thermal conductivity at 25°C	0.12 W x cm ⁻¹ x °K ⁻¹
Loss coefficient at 1064 nm	0.003 cm ⁻¹



Laser Properties

Laser Transition	⁴ I _{11/2} to ⁴ I _{13/2}
Laser Wavelength	2940nm
Fluorescence Lifetime	90 m s
Photon Energy	6.75×10 ⁻²⁰ J(@2940nm)
Emission Cross Section	3×10 ⁻²⁰ cm ²
Index of Refraction	1.79 @2940nm
Pump Bands	600~800 nm

Standard specifications

Dopant concentration, at. %	Up to 50
Orientation:	<111>within 5°
Flatness	< λ/10 measured at 633 nm
Parallelism	≤ 30"
Perpendicularity	≤ 5'
Surface Quality	10-5 per scratch-dig MIL-O-13830A
Optical Quality:	Interference fringes ≤ 0.125 λ /inch(@1064nm)
Extinction ration	≥ 25dB
Size:	Rods: Φ (3-10)mm ×(30-180)mm
Slabs:	(3-12)mm ×(6-24)mm ×(60-180)mm
Dimensional tolerances	Diameter:+0.000"/-0.05", Length: ± 0.05" Chamfer: 0.07+0.005/-0.00" at 45°
AR Coating Reflectivity	≤ 0.2% (@2940nm)

(Nd, Ce):YAG

Nd:Ce:YAG is an excellent laser material used for no-water cooling and miniature laser systems. the (Nd,Ce): YAG laser rod we produce has the characteristics of high efficiency(laser efficiency than Nd: YAG high about 30-50%), low threshold, anti-violet radiation and high repetition frequency for lasers operation. It has achieved the international advanced level .it is the most ideal laser material for the high repetition air cooling lasers. It suitable for different modes of operation (cw, pulsed , Q-switched, mode locked, doubling of frequency) and high-average power lasers

Physical and Chemical Properties

Chemical formula	$Nd^{3+}:Ce^{3+}:Y_3Al_5O_{12}$
Crystal Structure	Cubic
Lattice Parameters	12.01Å
Melting Point	1970 °C
Moh Hardness	8.5
Density	$4.56 \pm 0.04 \text{g/cm}^3$
Specific Heat (0-20)	$0.59 \text{J/g} \cdot \text{cm}^3$
Modulus of Elasticity	310GPa
Young's Modulus	$3.17 \times 10^4 \text{Kg/mm}^2$
Poisson Ratio	0.3(est.)
Tensile Strength	0.13~0.26GPa
Thermal Expansion Coefficient	[100]: $8.2 \times 10^{-6}/^\circ\text{C}$ [110]: $7.7 \times 10^{-6}/^\circ\text{C}$ [111]: $7.8 \times 10^{-6}/^\circ\text{C}$
Thermal Conductivity	14W/m/K(@25 °C)
Thermal Optical Coefficient (dn/dT)	$7.3 \times 10^{-6}/^\circ\text{C}$
Thermal Shock Resistance	790W/m



Laser Properties

Laser Transition	$^4F_{3/2} \rightarrow ^4I_{11/2}$
Laser Wavelength	1.064μm
Photon Energy	$1.86 \times 10^{-19} \text{J}@1.064\mu\text{m}$
Emission Linewidth	4.5Å @1.064μm
Emission Cross Section	$2.7 \sim 8.8 \times 10^{-19} \text{cm}^2$
Fluorescence Lifetime	230μs
Index of Refraction	1.8197@1064nm

Standard Specifications

Dopant concentration, at. %	0.1-2.5%
orientation:	<111>within 5°
Flatness	< λ/10
Parallelism	≤ 10"
Perpendicularity	≤ 5'
Surface quality	10-5 per scratch-dig MIL-O-13830A
Optical Quality:	Interference fringes ≤ 0. 25λ /inch Extinction ration ≥ 30dB
Size:	Diameter:3~8mm; Length:40~80mm(Upon request of customer)
Dimensional tolerances	Diameter+0.000"/-0.05"; Length ±0.5"; Chamfer: 0.07+0.005/-0.00" at 45°
AR Coating Reflectivity	≤ 0.2% (@1064nm)

Yb:YAG - Ytterbium Doped Yttrium Aluminum Garnets

Ytterbium doped Yttrium Aluminum Garnet (Yb:Y₃Al₅O₁₂ or Yb:YAG) is one of the most promising laser-active materials and more suitable for diode-pumping than the traditional Nd-doped crystals. It can be pumped at 0.94 μm and generates 1.03 μm laser output. Compared with the commonly used Nd:YAG crystal, Yb:YAG crystal has a larger absorption bandwidth in order to reduce thermal management requirements for diode lasers, a longer upper-state lifetime, three to four times lower thermal loading per unit pump power. Yb:YAG crystal is expected to replace Nd:YAG crystal for high power diode-pumped lasers and other potential applications, such as, its doubling wavelength is 515 nm very close to that of Ar-ion laser (514 nm), which makes it possible to replace large volume Ar-ion laser.

Physical and Chemical Properties

Chemical formula	Yb ³⁺ :Y ₃ Al ₅ O ₁₂
Crystal structure	cubic
Lattice Parameters	12.01Å
Melting Point	1970 °C
Density, g/cm ³	4.56
Mohs hardness	8.5
Thermal expansion coefficient	7.8 x 10 ⁻⁶ x °K ⁻¹ , <111>, 0 - 250 °C 7.7x10 ⁻⁶ / °C, <110> (0~250 °C) 8.2x10 ⁻⁶ / °C, <100> (0~250 °C)
Thermal conductivity at 25°C	0.14 W x cm ⁻¹ x °K ⁻¹
Loss coefficient at 1064 nm	0.003 cm ⁻¹

Laser Properties

Laser Transition	² F _{5/2} → ² F _{7/2}
Laser Wavelength	1030nm
Photon Energy	1.93x10 ⁻¹⁹ J(@1030nm)
Emission Linewidth	9nm
Emission Cross Section	2.0x10 ⁻²⁰ cm ²
Fluorescence Lifetime	1.2 ms

Spectral Properties

Diode Pump Band	940nm or 970nm
Thermal Optical Coefficient	7.3x10 ⁻⁶ / °C
Index of Refraction	1.82

Standard Specifications

Dopant concentration, at. %	0.5-30%
orientation:	<111>within 5°
Flatness	< λ/10
Parallelism	≤ 10"
Perpendicularity	≤ 5'
Surface Quality	10-5(MIL-O-13830A)
Optical Quality:	Interference fringes ≤ 0.125/inch, Extinction ration ≥ 30dB
Size:	Diameter:2 ~ 20mm,Length:5 ~ 150mm (Upon request of customer)
Dimensional tolerances	Diameter:+0.00"/-0.05"mm; Length: ± 0.02" ; Chamfer: 0.07+0.005/-0.00" at 45°
AR Coating Reflectivity	≤ 0.2% (@1030nm)

Cr⁴⁺:YAG

Cr⁴⁺:Y₃Al₅O₁₂ - Passive Q-switches or saturable absorbers provide high power laser pulses without electro-optic Q-switches, thereby reducing the package size and eliminating a high voltage power supply. Cr⁴⁺:YAG is more robust than dyes or color centers and is the material of choice for 1 um Nd lasers.

Physical and Chemical Properties

Formula	Cr ⁴⁺ :Y ₃ Al ₅ O ₁₂
Crystal structure	cubic
Mohs hardness	8.5
Melting point:	1970 °C
Density, g/cm ³	4.55
Thermal conductivity at 25°C	0.14 W x cm ⁻¹ x °K ⁻¹
Thermal expansion coefficient	7.8 x 10 ⁻⁶ / °C <111> 8.2 x 10 ⁻⁶ / °C <100> 7.7x10 ⁻⁶ / °C <110>
Young's Modulus	3.17x10 ⁴ kg/mm ²
Thermal Shock Resistance	790 Wm ⁻¹

Standard Specifications

Orientation:	<111>within 5° or <100>within 5°
Flatness	< λ/10
Parallelism	≤ 30"
Perpendicularity	≤ 5'
Surface quality	20-10(MIL-O-13830A))
Wavelength:	950 nm ~ 1100nm
Initial transmittance:	5%~95%
Damage threshold	≥ 500MW/cm ²
AR coating reflectivity	≤ 0.2% (@1064nm)
Size	Diameter:3 ~ 20mm H x W:3 x 3 ~ 20 x 20mm
Dimensional tolerances	Diameter: ± 0.00/-0.05", Length: ± 0.05" Chamfer: 0.07+0.005/-0.00" at 45°

KTP Crystal

Advantages:

- large nonlinear optical coefficient
- wide angular bandwidth and small walk-off angle
- broad temperature and spectral bandwidth
- high electro-optic coefficient and low dielectric constant
- large figure of merit
- nonhygroscopic, chemically and mechanically stable

Applications:

- frequency doubling (SHG) of Nd-doped lasers for green/red output.
- frequency mixing (SFM) of Nd laser and diode laser for blue output.
- parametric sources (OPG, OPA and OPO) for 600nm-4500nm tunable output.
- E-O modulators, optical switches, directional couplers.
- optical waveguides for integrated NLO and E-O devices.

Using advanced technique in crystal growth, 35x55x68mm³ transparent KTP boule with flux method has been grown. As large as 15x15x20mm³ KTP devices are fabricated.

We provide KTP with:

- strict quality control on optical homogeneity, transmission and scattering
- quick delivery
- unbeatable price and quantity discount
- technical support
- AR-coating, mounting and re-polishing service

Structural and Physical Properties:

Crystal structure	Orthorhombic, space group Pna21, point group mm2
Cell parameters	a=6.404 Angstrom, b=10.616 Angstrom, c=12.814 Angstrom, Z=8
Melting point	1172° C incongruent
Curie point	936° C
Mohs hardness	≈5
Density	3.01 g/cm ³
Color	colorless
Hygroscopic susceptibility	no
Specific heat	0.1643 cal/g°C
Thermal conductivity	0.13 W/cm/°K
Electrical conductivity	3.5x10 ⁻⁸ s/cm (c-axis, 22° C, 1KHz)

Nonlinear Optical Properties:

Phase matchable SHG range:	497 - 1800nm
Nonlinear optical coefficients:	d ₃₁ =6.5pm/v, d ₃₂ =5pm/v, d ₃₃ =13.7pm/v, d ₂₄ =7.6pm/v, d ₁₅ =6.1pm/v d _{eff} (II) ≈ (d ₂₄ - d ₁₅)sin2φ sin2θ - (d ₁₅ sin2φ + d ₂₄ cos2φ)sinθ
For type II SHG of a Nd:YAG laser at 1064nm:	PM angle: θ=90°, φ =23.3° Effective SHG coefficient: d _{eff} ≈8.3xd ₃₆ (KDP) Angular acceptance: 20 mrad-cm Temperature acceptance: 25° C-cm Spectral acceptance: 5.6 Angstrom -cm Walk-off angle: 4.5 mrad (0.26°) Damage threshold: >450MW/cm ² @1064nm, 10ns, 10Hz
Electro-optic coefficients: r ₁₃	Low frequency (pm/V) High frequency (pm/V) 9.5 8.8

r ₂₃	15.7 13.8
r ₃₃	36.3 35.0
r ₅₁	7.3 6.9
r ₄₂	9.3 8.8
Dielectric constant:	e _{eff} =13

Optical Properties:

Transmitting range:	350 nm - 4500 nm
Refractive indices:	n _x n _y n _z
1064nm	1.7377 1.7453 1.8297
532nm	1.7780 1.7886 1.8887
Therm-optic coefficients:	dn _x /dT=1.1x10 ⁻⁵ /° C, dn _y /dT=1.3x10 ⁻⁵ /° C, dn _z /dT=1.6x10 ⁻⁵ /° C
Absorption	α < 1% cm ⁻¹ @1064nm and 532nm

Applications for SHG and SFG of Nd:lasers

KTP is the most commonly used material for frequency doubling of Nd:YAG lasers and other Nd-doped lasers, particularly at the low or medium power density. To date, extra- and intra-cavity frequency doubled Nd:lasers using KTP have become a preferred source of pumping visible dye lasers and tunable Ti:Sapphire lasers as well as their amplifiers. Applied to diode-pumped Nd:laser, KTP has provided the basis for the construction of compact visible solid state laser systems.

Recent advances in intracavity-doubled Nd:YAG and Nd:YVO4 lasers, have increased the demand for compact green lasers used in optical disk and laser printer. Over 100mW and 76mW TEM00 green outputs are available from LD pumped Nd:YAG and Nd:YVO4 lasers, respectively. Moreover, 2.5mW green light has derived from 50mW LD pumped and intracavity doubled Nd:YVO4 mini-lasers with a 9mm long cavity.

KTP has also shown its powerful applications in extracavity SHG with conversion efficiency exceeding 60%. The applications of KTP for intracavity mixing of 810nm diode and 1064nm Nd:YAG laser to generate blue light and intracavity SHG of Nd:YAG or Nd:YAP lasers at 1300nm to produce red light are also in progress.

Applications for OPG, OPA and OPO

As an efficient OPO crystal pumped by a Nd:laser and its second harmonics, KTP plays an important role for parametric sources for tunable output from visible (600nm) to mid-IR (4500nm). KTP's OPO results in stable, continuous outputs of femtosecond pulse of 108 Hz repetition rate and milliwatt average power levels in both signal and idler output. KTP's OPO pumped by a 1064nm Nd:YAG laser has generated above 66% efficiency for degenerately converting to 2120nm.

KTP Specifications

- Transmitting wavefront distortion: less than $\lambda / 4$ @ 633 nm
- Dimension tolerance: (W ± 0.1 mm) x (H ± 0.1 mm) x (L + 0.2 mm/-0.1mm)
- Clear aperture: > 90% central area
- Flatness: $\lambda / 8$ @ 633 nm
- Scratch/Dig code: 10/5 to MIL-O-13830A
- Parallelism: better than 20 arc seconds
- Perpendicularity: 5 arc minutes
- Angle tolerance: $\Delta\theta < \pm 0.5^\circ$, $\Delta\phi < \pm 0.5^\circ$
- AR coating: R < 0.2% at 1064nm and R < 1.0% at 532 nm.
- Quality Warranty Period: one year under proper use.

LBO

Lithium Triborate (LiB₃O₅ or LBO) is an excellent nonlinear optical crystal and it has the following features:

- * broad transparency range from 160nm to 2600nm
- * high optical homogeneity ($\delta n \approx 10^{-6}$) and being free of inclusion
- * relatively large effective SHG coefficient (about three times that of KDP)
- * high damage threshold
- * wide acceptance angle and small walk-off
- * type I and type II non-critical phase matching (NCPM) in a wide wavelength range
- * spectral NCPM near 1300nm.

We can provide LBO crystals:

- * large crystal size up to 30x30x30mm³ and maximum length of 60mm
- * AR-coating, mounts and re-polishing services
- * a large quantity of crystals in stock
- * fast delivery(10 days for polished only, 15 days for AR-coated).

Table 1. Chemical and Structural properties

Crystal Structure	Orthorhombic, Space group Pna21, Point group mm2
Lattice Parameter	a=8.4473Å, b=7.3788Å, c=5.1395Å, Z=2
Melting Point	About 834°C
Mohs Hardness	6
Density	2.47 g/cm ³
Thermal Conductivity	3.5W/m/K
Thermal Expansion Coefficient	ax=10.8x10 ⁻⁵ /K, ay= -8.8x10 ⁻⁵ /K, az=3.4x10 ⁻⁵ /K

Table 2. Optical and Nonlinear Optical Properties

Transparency Range	160-2600nm
SHG Phase Matchable Range	551 ~ 2600nm (Type I) 790-2150nm (Type II)
Therm-optic Coefficient (°C, l in μm)	dn _x /dT=-9.3X10 ⁻⁶ dn _y /dT=-13.6X10 ⁻⁶ dn _z /dT=(-6.3-2.1l)X10 ⁻⁶
Absorption Coefficient	<0.1%/cm at 1064nm <0.3%/cm at 532nm
Angle Acceptance	6.54mrad-cm (φ, Type I, 1064 SHG) 15.27mrad-cm (q, Type II, 1064 SHG)
Temperature Acceptance	4.7°C-cm (Type I, 1064 SHG) 7.5°C-cm (Type II, 1064 SHG)
Spectral Acceptance	1.0nm-cm (Type I, 1064 SHG) 1.3nm-cm (Type II, 1064 SHG)
Walk-off Angle	0.60° (Type I, 1064 SHG) 0.12° (Type II, 1064 SHG)
NLO Coefficient	d _{eff} (I)=d ₃₂ cosφ (Type I in XY plane) d _{eff} (I)=d ₃₁ cos2θ+d ₃₂ sin2θ (Type I in XZ plane) d _{eff} (II)=d ₃₁ cosθ (Type II in YZ plane) d _{eff} (II)=d ₃₁ cos2θ+d ₃₂ sin2θ (Type II in XZ plane)
Non-vanished susceptibilities	NLO d ₃₁ =1.05 ± 0.09 pm/V d ₃₂ = -0.98 ± 0.09 pm/V d ₃₃ =0.05 ± 0.006 pm/V
Sellmeier Equations(λ in μm)	n _x ² =2.454140+0.011249/(λ ² -0.011350)-0.014591λ ² -6.60x10 ⁻⁵ λ ⁴ n _y ² =2.539070+0.012711/(λ ² -0.012523)-0.018540λ ² +2.0x10 ⁻⁴ λ ⁴ n _z ² =2.586179+0.013099/(λ ² -0.011893)-0.017968λ ² -2.26x10 ⁻⁴ λ ⁴

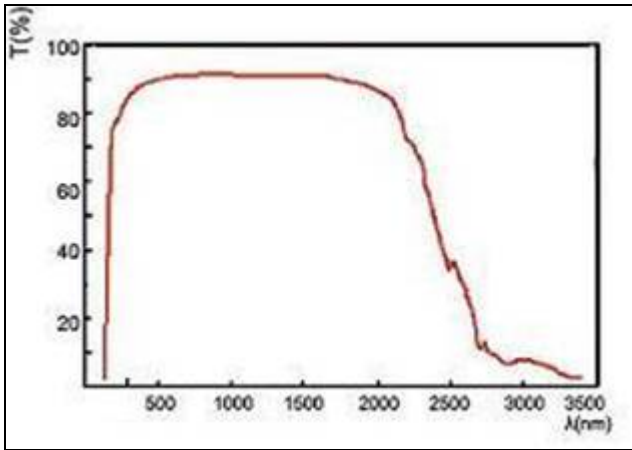


Figure 1. Transparency curve of LBO

SHG and THG at Room Temperature

LBO is phase matchable for the SHG and THG of Nd:YAG and Nd:YLF lasers, using either type I or type II interaction. For the SHG at room temperature, type I phase matching can be reached and has the maximum effective SHG coefficient in the principal XY and XZ planes (see Fig. 2) in a wide wavelength range from 551nm to about 2600nm. The optimum type II phase matching falls in principal YZ and XZ planes(see Fig 2).

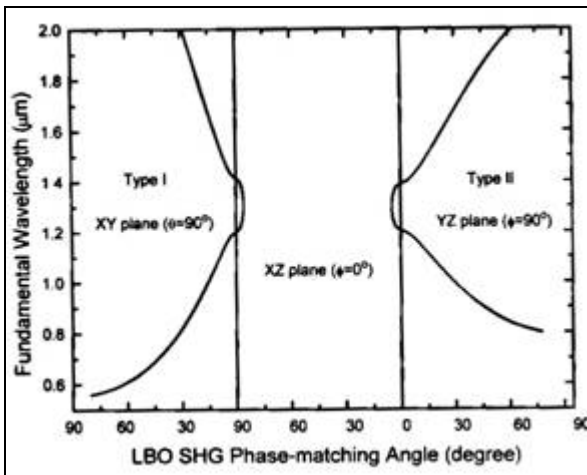


Figure 2. Optimum matching

SHG conversion efficiencies of more than 70% for pulse and 30% for cw Nd:YAG lasers, and THG conversion efficiency over 60% for pulse Nd:YAG laser have been observed.

Applications:

- More than 480mW output at 395nm is generated by frequency doubling a 2W mode-locked Ti:Sapphire laser (<2ps, 82MHz). The wavelength range of 700-900nm is covered by a 5x3x8mm³ LBO crystal.
- Over 80W green output is obtained by SHG of a Q-switched Nd:YAG laser in a type II 18mm long LBO crystal.
- The frequency doubling of a diode pumped Nd:YLF laser (>500μJ @ 1047nm, <7ns, 0-10KHz) reaches over 40% conversion efficiency in a 9mm long LBO crystal.
- The VUV output at 187.7 nm is obtained by sum-frequency generation.
- 2mJ/pulse diffraction-limited beam at 355nm is obtained by intra-cavity frequency tripling a Q-switched Nd:YAG laser.

Non-Critical Phase-Matching

Table 3. Properties of type I NCPM SHG at 1064nm

NCPM Temperature	148°C	
Acceptance Angle	52	mrad-cm ^{1/2}
Walk-off Angle	0	
Temperature Bandwidth	4°C-cm	
Effective SHG Coefficient	2.69 d ₃₆ (KDP)	

AS shown in table 3, Non-Critical Phase-Matching (NCPM) of LBO is featured by no walk-off, very wide acceptance angle and maximum effective coefficient. It promotes LBO to work in its optimal condition. SHG conversion efficiencies of more than 70% for pulse and 30% for cw Nd:YAG lasers have been obtained, with good output stability and beam quality.

As shown in Fig.3, type I and type II non-critical phase-matching can be reached along x-axis and z-axis at room temperature, respectively.

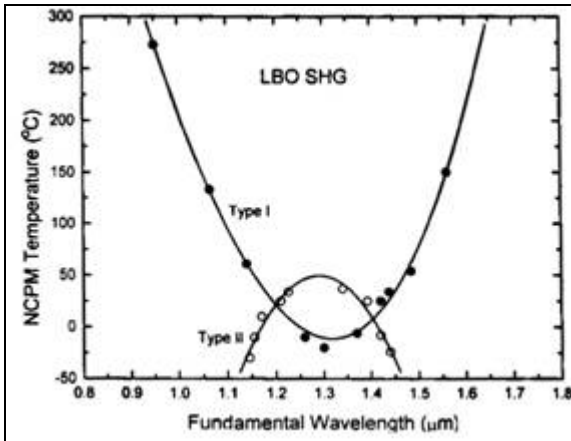


Figure 3. NCPM temperature tuning curves of LBO

Applications:

- Over 11W of average power at 532nm was obtained by extra-cavity SHG of a 25W Antares mode-locked Nd:YAG laser (76MHz, 80ps).
- 20W green output was generated by frequency doubling a medical, multi-mode Q-switched Nd:YAG laser. Much higher green output is expected with higher input.

LBO's OPO and OPA

LBO is an excellent NLO crystal for OPOs and OPAs with a widely tunable wavelength range and high powers. These OPO and OPA that are pumped by the SHG and THG of Nd:YAG laser and XeCl excimer laser at 308nm have been reported. The unique properties of type I and type II phase matching as well as the NCPM leave a big room in the research and applications of LBO's OPO and OPA. Fig.4 shows the calculated type I OPO tuning curves of LBO pumped by the SHG, THG and 4HG of Nd:YAG laser in XY plane at the room temperature. And Fig. 5 illustrates type II OPO tuning curves of LBO pumped by the SHG and THG of Nd:YAG laser in XZ plane.

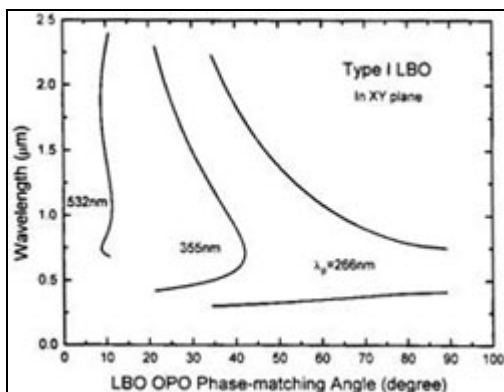


Figure 4. Type I OPO tuning curves of LBO

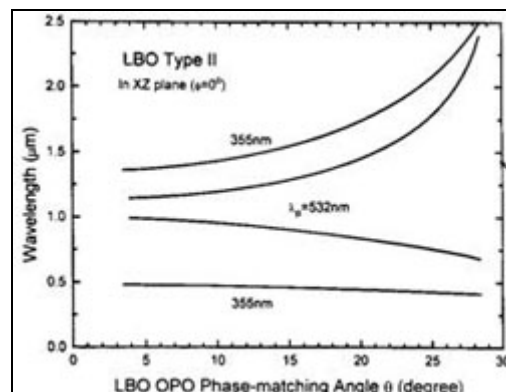


Figure 5. Type II OPO tuning curves of LBO

Applications:

- A quite high overall conversion efficiency and 540-1030nm tunable wavelength range were obtained with OPO pumped at 355nm.
- Type I OPA pumped at 355nm with the pump-to-signal energy conversion efficiency of 30% has been reported.

- Type II NCPM OPO pumped by a XeCl excimer laser at 308nm has achieved 16.5% conversion efficiency, and moderate tunable wavelength ranges can be obtained with different pumping sources and temperature tuning.
- By using the NCPM technique, type I OPA pumped by the SHG of a Nd:YAG laser at 532nm was also observed to cover a wide tunable range from 750nm to 1800nm by temperature tuning from 106.5°C to 148.5°C.
- By using type II NCPM LBO as an optical parametric generator (OPG) and type I critical phase-matched BBO as an OPA, a narrow linewidth (0.15nm) and high pump-to-signal energy conversion efficiency (32.7%) were obtained when it is pumped by a 4.8mJ, 30ps laser at 354.7nm. Wavelength tuning range from 482.6nm to 415.9nm was covered by increasing the temperature of LBO or rotating BBO.

LBO's Spectral NCPM

Not only the ordinary non-critical phase matching (NCPM) for angular variation but also the noncritical phase matching for spectral variation (SNCPM) can be achieved in the LBO crystal. As shown in Fig.2, the phase matching retracing positions are $\lambda_1=1.31\mu\text{m}$ with $\theta=86.4^\circ$, $\phi=0^\circ$ for Type I and $\lambda_2=1.30\mu\text{m}$ with $\theta=4.8^\circ$, $\phi=0^\circ$ for Type II. The phase matching at these positions possess very large spectral acceptances $\Delta\lambda$. The calculated $\Delta\lambda$ at λ_1 and λ_2 are 57nm-cm-1/2 and 74nm-cm-1/2 respectively, which are much larger than the other NLO crystals. These spectral characteristics are very suitable for doubling broadband coherent radiations near 1.3 μm , such as those from some diode lasers, and some OPA/OPO output without linewidth-narrowing components.

The crystal holder (free) and oven & Temperature Controller_(for NCPM,OPO,OPA applications) are available for BBO & LBO.

AR-coating

- Dual Band AR-coating (DBAR) of LBO for SHG of 1064nm.
 - low reflectance ($R<0.2\%$ at 1064nm and $R<0.5\%$ at 532nm);
 - high damage threshold ($>500\text{MW}/\text{cm}^2$ at both wavelengths);
 - long durability.
- * Broad Band AR-coating (BBAR) of LBO for SHG of tunable lasers.
- * Other coatings are available upon request.
- * Dimension tolerance: $(W\pm 0.1\text{mm})\times(H\pm 0.1\text{mm})\times(L+0.5/-0.1\text{mm})$ ($L\geq 2.5\text{mm}$)
 $(W\pm 0.1\text{mm})\times(H\pm 0.1\text{mm})\times(L+0.1/-0.1\text{mm})$ ($L< 2.5\text{mm}$)
- Clear aperture: central 90% of the diameter
- No visible scattering paths or centers when inspected by a 50mW green laser
- Flatness: less than $\lambda/8$ @ 633nm
- Transmitting wavefront distortion: less than $\lambda/8$ @ 633nm
- Chamfer: $\leq 0.2\text{mm}@450$
- Chip: $\leq 0.1\text{mm}$
- Scratch/Dig code: better than 10/ 5 to MIL-O-13830A
- Parallelism: better than 20 arc seconds
- Perpendicularity: ≤ 5 arc minutes
- Angle tolerance: $\Delta\theta\leq 0.25^\circ$, $\Delta\phi\leq 0.25^\circ$
- Damage threshold[GW/cm]: >10 for 1064nm, TEM00, 10ns, 10HZ (polished only)
 >1 for 1064nm, TEM00, 10ns, 10HZ (AR-coated)
 >0.5 for 532nm, TEM00, 10ns, 10HZ (AR-coated)
- Quality Warranty Period: one year under proper use.

NOTE

1. LBO has a very low susceptibility to moisture. Users are advised to provide dry conditions for both the use and preservation of LBO.
2. Polished surfaces of LBO requires precautions to prevent any damage.
3. We can select and design the best crystal for you, if the main parameters of your laser are provided, such as energy per pulse, pulse width and repetition rate for a pulsed laser, power for a cw laser, laser beam diameter, mode condition, divergence, wavelength tuning range, etc.

Beta-Barium Borate (β -BaB₂O₄, BBO)

Main features are:

- Broad phase-matchable range from 409.6 nm to 3500nm;
- Wide transmission region from 190 nm to 3500nm;
- Large effective second-harmonic-generation (SHG) coefficient about 6 times greater than that of KDP crystal;
- High damage threshold of 10GW/cm² for 100ps pulse-width at 1064nm;
- High optical homogeneity with $\delta n \approx 10^{-6}/\text{cm}$;
- Wide temperature-bandwidth of about 55°C.

We offer:

- Strict quality control;
- Crystal length from 0.02mm to 25mm and size up to 15x15x15 mm³;
- P-coatings, AR-coatings, mounts and re-polishing services;
- A large quantity of crystals in stock
- Fast delivery (10 days for polished only, 15 days for AR-coated).

Basic Properties

Table 1. Chemical and Structural properties

Crystal Structure:	Trigonal, space group R3c
Lattices Parameters:	a=b=12.532Å, c=12.717Å, Z=6
Melting point	About 1095°C
Mohs Hardness	4
Density	3.85g/cm ³
Thermal Conductivity	1.2W/m/K(\perp c): 1.6w/m/K(\parallel c)
Thermal Expansion Coefficients	α ,4x10 ⁻⁶ /K; c,36x10 ⁻⁶ /K

Table 2. Optical and Nontinear Optical Properties

Transparency Range:	190-3500nm
SHG Phase Matchable Range	409.6-3500nm(Type I) 525-3500nm(Type II)
therm-optic Coefficients(/°C)	$dn_o/dT = -9.3 \times 10^{-6}/^\circ\text{C}$ $dn_e/dT = -16.6 \times 10^{-6}/^\circ\text{C}$
Absorption Coefficients	<0.1%/cm at 1064nm <1%/cm at 532nm
Angle Acceptance	0.8mrad-cm (θ , Type I, 1064 SHG) 1.27mrad-cm (θ , Type II, 1064 SHG)
Temperature Acceptance	55°C-cm
Spectral Acceptance	1.1nm-cm
Walk-off Angle	2.7° (Type I 1064 SHG) 3.2° (Type II 1064 SHG)
NLO Coefficients	$d_{\text{eff}}(\text{I}) = d_{31} \sin\theta + (d_{11} \cos\Phi - d_{22} \sin 3\Phi) \cos\theta$ $d_{\text{eff}}(\text{II}) = (d_{11} \sin 3\Phi + d_{22} \cos 3\Phi) \cos^2\theta$
Non-vanished NLO susceptibilities	$d_{11} = 5.8 \times d_{36}(\text{KDP})$ $d_{31} = 0.05 \times d_{11}$ $d_{22} < 0.05 \times d_{11}$
sellmeier Equations(λ in μm)	$n_o^2 = 2.7359 + 0.01878 / (\lambda^2 - 0.01822) - 0.01354 \lambda^2$ $n_e^2 = 2.3753 + 0.01224 / (\lambda^2 - 0.01667) - 0.01516 \lambda^2$
Electro-optic coefficients:	$r_{11} = 2.7 \text{ pm/V}$, r_{22} , $r_{31} < 0.1 \nu_{11}$
Half-wave voltage:	7KV (at 1064nm, 3*3*20mm3)
Resistivity:	>10 ¹¹ ohm-cm
Relative Dielectric Constant:	$\epsilon_{11}^s / \epsilon_0: 6.7$ $\epsilon_{33}^s / \epsilon_0: 8.1$ Tan $\delta < 0.001$

BBO is a negative uniaxial crystal, with ordinary refractive-index(n_o) larger than extraordinary refractive-index(n_e). Both type I and type II phase-matching can be reached by angle-tuning. The phase matching angles of frequency doubling are shown in Fig.2.

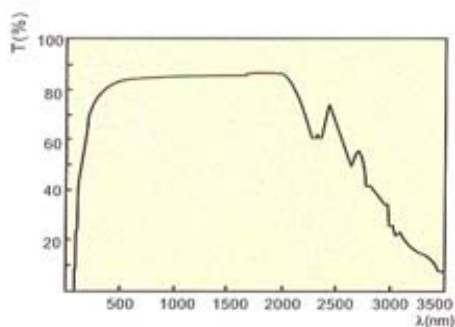


Figure 1. Transparency curve of BBO

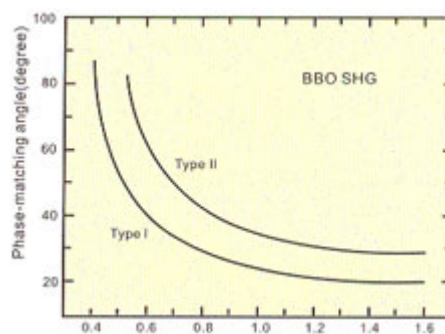


Figure 2. SHG tuning curves of BBO

Application in Nd:YAG Lasers

BBO is an efficient NLO crystal for the second, third and fourth harmonic generation of Nd:YAG lasers, and the best NLO crystal for the fifth harmonic generation at 213 nm. Conversion efficiencies of more than 70% for SHG, 60% for THG and 50% for 4HG, and 200 mW output at 213 nm (5HG) have been obtained, respectively.

BBO is also an efficient crystal for the intracavity SHG of high power Nd:YAG lasers. For the intracavity SHG of an acousto-optic Q-switched Nd:YAG laser, more than 15 W average power at 532 nm was generated in a AR-coated BBO crystal. When pumped by the 600 mW SHG output of a mode-locked Nd:YLF laser, 66 mW output at 266 nm was produced from a Brewster-angle-cut BBO in an external enhanced resonant cavity.

Because of a small acceptance angle and large walk-off, good laser beam quality (small divergence, good mode condition, etc.) is the key for BBO to obtain high conversion efficiency. Tight focus of laser beam is not recommended by our engineers.

Applications in Tunable Lasers

1. Dye lasers

Efficient UV output (205 nm–310 nm) with a SHG efficiency of over 10% at wavelength of ≥ 206 nm was obtained in type I BBO, and 36% conversion efficiency was achieved for a XeCl-laser pumped Dye laser with power 150 kW which is about 4–6 times higher than that in ADP. The shortest SHG wavelength of 204.97 nm with efficiency of about 1% has been generated.

Our BBO is widely used in the Dye lasers. With type I sum-frequency of 780–950 nm and 248.5 nm (SHG output of 495 nm dye laser) in BBO, the shortest UV outputs ranging from 188.9 nm to 197 nm and the pulse energy of 95 mJ at 193 nm and 8 mJ at 189 nm have been obtained, respectively.

2. Ultrafast Pulse Laser

Frequency-doubling and -tripling of ultrashort-pulse lasers are the applications in which BBO shows superior properties to KDP and ADP crystals. Now, we can provide as thin as 0.02 mm BBO for this purpose. A laser pulse as short as 10 fs can be efficiently frequency-doubled with a thin BBO, in terms of both phase-velocity and group-velocity matching.

3. Ti:Sapphire and Alexandrite lasers

UV output in the region 360 nm–390 nm with pulse energy of 105 mJ (31% SHG efficiency) at 378 nm, and output in the region 244 nm–259 nm with 7.5 mJ (24% mixing efficiency) have been obtained for type I SHG and THG of an Alexandrite laser in BBO crystal.

More than 50% of SHG conversion efficiency in a Ti:Sapphire laser has been obtained. High conversion efficiencies have been also obtained for the THG and FHG of Ti:Sapphire lasers.

4. Argon Ion and Copper-Vapor lasers

By employing the intracavity frequency-doubling technique in an Argon Ion laser with all lines output power of 2 W, maximum 33 mW at 250.4 nm and thirty-six lines of deep UV wavelengths ranging from 228.9 nm to 257.2 nm were generated in a Brewster-angle-cut BBO crystal.

Up to 230 mW average power in the UV at 255.3 nm with maximum 8.9% conversion efficiency was achieved for the SHG of a Copper-Vapor laser at 510.6 nm.

BBO's OPO and OPA

The OPO and OPA of BBO are powerful tools for generating a widely tunable coherent radiation from the UV to IR. The tuning angles of type I and type II BBO OPO and OPA have been calculated, with the results shown in Fig.5 and Fig.6, respectively.

1.OPO pumped at 532 nm

an OPO output ranging from 680 nm to 2400 nm with the peak power of 1.6MW and up to 30% energy conversion efficiency was obtained in a 7.2 mm long type I BBO. The input pump energy was 40 mJ at 532nm with pulse-width 75ps. With a longer crystal, higher conversion efficiency is expected.

2.OPO and OPA pumped at 355 nm

In the case of Nd:YAG pumping,BBO's OPOs can generate more than 100mJ,with wavelength tunable from 400nm to 2000nm. Using our BBO crystal, the OPO system covers a tuning range from 400nm to 3100nm which guarantees a maximum of 30% and more than 18% conversion efficiency, over the wavelength range from 430nm to 2000nm.

Type II BBO can be used to decrease linewidth near the degenerate points. A linewidth as narrow as 0.05nm and usable conversion efficiency of 12% were obtained. However, a longer (>15mm) BBO should normally be used to decrease the oscillation threshold when employing the type II phase-matching scheme.

Pumping with a picosecond Nd:YAG at 355nm, a narrow-band(<0.3nm), high energy (>200μJ) and wide tunable (400nm to 2000nm) pulse has been produced by BBO's OPAs. This OPA can reach as high as more than 50% conversion efficiency, and therefore is superior to common Dye lasers in many respects, including efficiency, tunable range, maintenance, and easiness in design and operation. Furthermore, coherent radiation from 205 nm to 3500 nm can be also generated by BBO's OPO or OPA plus a BBO for SHG.

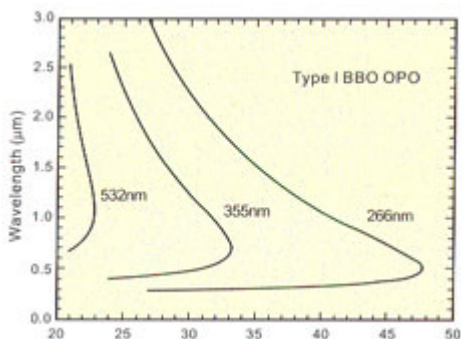


Figure3.Type I OPO tuning curves of BBO

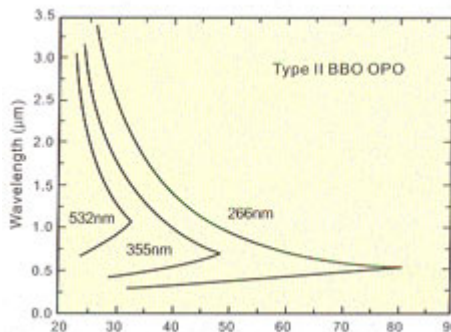


Figure4,Type II OPO tuning curves of BBO

3.Others

A tunable OPO with signal wavelengths between 422 nm and 477 nm has been generated by angle tuning in a type I BBO crystal pumped by the fourth harmonic of a Nd:YAG laser (at 266 nm) has been observed to cover the whole range of output wavelengths 330 nm -1370nm.

When pumped by a 1mJ, 80fs Dye laser at 615 nm,the OPA with two BBO crystals yields more than 50μJ (maximum 130μJ),<200fs ultrashort pulse, over 800 nm-2000 nm.

BBO's E-O Applications

BBO can also be used for E-O applications. It has wide transmission range from UV to about 3500nm and it has much higher damage threshold than KD*P or LiNbO₃, More than 80W output power and 50KHZ repetition rate have been reached by using our E-O BBO crystals and Nd:YVO₄ crystals as gain media. At 5K Hz, its pulse has width as short as 6.4ns,and energy of 5.7mJ or peak power of 900 KW.It has advantages over the commercial A-O Q-switched one , including a very short pulse,high beam quality and size compact as well. Although it has a relative small electro-optic coefficient,the Half-wave voltage is high (7KV at 1064nm,3*3*20mm³),long and thin BBO can reduce the voltage requirements.

We now can supply 25mm long and 1mm thin high optica quality of BBO crystal with Z-cut, AR-coated and Gold/Chrome plated on the side faces.

Coatings

We provide the following AR-coatings for BBO:

- Dual Band AR-coating (DBAR)of BBO for SHG of 1064nm
 1. low reflectance ($R < 0.2\%$ at 1064nm and $R < 0.5\%$ at 532nm);
 2. high damage threshold ($> 300\text{MW}/\text{cm}^2$ at both wqvelengths);
 3. long durability;
- Broad Band AR-coating (BBAR) of BBO for SHG of tunable lasers.
- Broad Band P-coating of BBO for OPO applications.
- Other coatings are available upon request.

Warranty on BBO Specifications

- Dimension tolerance:
($W \pm 0.1\text{mm}$) \times ($H \pm 0.1\text{mm}$) \times ($L + 0.5/-0.1\text{mm}$) ($L \geq 22.2.5\text{mm}$)
($W \pm 0.1\text{mm}$) \times ($H \pm 0.1\text{mm}$) \times ($L + 0.1/-0.1\text{mm}$) ($L < 2.5\text{mm}$)
- Clear aperture :central 90% or the diameter
- No visible scattering paths or centers when inspected by a 50mW green Laser
- Flatness: less than $\lambda/8$ @ 633nm
- Transmitting wavefront distortion: less than $\lambda/8$ @ 633nm
- Chamfer: $\leq 0.2\text{mm}$ @ 45°
- Chip: $\leq 0.1\text{mm}$
- Scratch/Dig code: better than 10/5 to MIL-O-13830A
- Parallelism: ≤ 20 arc seconds
- Perpendicularity: ≤ 5 arc minutes
- Angle tolerance: $\leq 0.25^\circ$, $\leq 0.25^\circ$
- Damage threshold{GW/cm}:
>1for1064nm,TEM00,10ns,10HZ (polished only),
>0.5 for 1064nm,TEM00,10ns,10HZ(AR-coated) ;
>0.3 for 532nm,TEM00,10ns,10HZ(AR-coatd)

Note

- BBO has a low susceptibility to the moisture. The user is advised to provide dry conditions for both the use and preservation of BBO.
- BBO is relatively soft and therefore requires precautions to protect its polished surfaces.
- When angle adjusting is necessary, keep in mind that the acceptance angle of BBO is small.
- Our engineers can select and design the best crystal, if the main parameters of your laser are provided, such as energy per pulse, pulse width and repetition rate for a pulsed laser, power for a cw laser, laser beam diameter, mode condition, divergence, wavelength tuning range, etc.

KTA (Potassium Titanyl Arsenate, KTiOAsO_4)

KTA crystal features large non-linear optical and electro-optical coefficients in comparison to KTP and has the added benefit of significantly reduced absorption in the 2 to 5 μm region. It has found more and more applications in second harmonic generation (SHG), sum and difference frequency generation (SFG)/(DFG), optical parametric oscillation/ amplification (OPO/OPA), and electro-optical Q-switching.

KTA features

- Large nonlinear optical coefficients
- Wide angular bandwidth and small walk-off angle
- Broad temperature and spectral bandwidth
- Large electro-optic coefficients
- Lower absorption in the 3-4 μm range than KTP.
- Nonhygroscopic, chemically and mechanically stable
- High thermal conductivity
- High damage threshold

KTA is a positive biaxial crystal, with the principal axes X, Y, and Z ($n_z > n_y > n_x$) parallel to the crystallographic axes a, b, and c, respectively.

Structural and Physical Properties

Crystal Structure	Orthorhombic, space group $\text{Pna}2_1$, point group $\text{mm}2$
Cell Parameters	$a=13.125\text{\AA}$, $b=6.5716\text{\AA}$, $c=10.786\text{\AA}$, $Z=8$
Melting Point	1130oC
Curie Point	880oC
Mohs Hardness	~ 5
Density	3.45 g/cm ³
Color	colorless
Hygroscopic Susceptibility	No
Specific Heat	0.687 J/g/K
Thermal Conductivity	1.8 W/m/K
Electrical Conductivity	$0.7\text{-}3.4 \times 10^{-6}$ s/cm (c-axis, @22 oC, 1KHz)

Linear Optical Properties:

Transmitting Range	350 nm - 5500 nm												
Refractive Indices: 1064nm 532nm	<table style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th style="width: 33%;"></th> <th style="width: 33%; text-align: center;">nx</th> <th style="width: 33%; text-align: center;">ny</th> <th style="width: 33%; text-align: center;">nz</th> </tr> </thead> <tbody> <tr> <td></td> <td style="text-align: center;">1.7818</td> <td style="text-align: center;">1.7866</td> <td style="text-align: center;">1.8680</td> </tr> <tr> <td></td> <td style="text-align: center;">1.8264</td> <td style="text-align: center;">1.8331</td> <td style="text-align: center;">1.9310</td> </tr> </tbody> </table>		nx	ny	nz		1.7818	1.7866	1.8680		1.8264	1.8331	1.9310
	nx	ny	nz										
	1.7818	1.7866	1.8680										
	1.8264	1.8331	1.9310										
Sellmeier Equations (l in μm)	$n_x^2 = 1.90713 + 1.23522l^2 / (l^2 - 0.19692) - 0.01025l^2$ $n_y^2 = 2.15912 + 1.00099l^2 / (l^2 - 0.21844) - 0.01096l^2$ $n_z^2 = 2.14768 + 1.29559l^2 / (l^2 - 0.22719) - 0.01436l^2$												
Thermo-optic Coefficients	$dn_x/dT = 1.1 \times 10^{-5}/\text{oC}$, $dn_y/dT = 1.3 \times 10^{-5}/\text{oC}$ $dn_z/dT = 1.6 \times 10^{-5}/\text{oC}$												
Absorption Coefficient	$a < 1\% \text{ cm}^{-1}$ @1064nm and 532nm												

Nonlinear Optical Properties:

Phasematchable SHG Range	542 - 1800nm
Nonlinear Optical Coefficients	$d_{31} = 2.8 \text{ pm/v}$, $d_{32} = 4.2 \text{ pm/v}$, $d_{33} = 16.2 \text{ pm/v}$, $d_{24} = 3.2 \text{ pm/v}$, $d_{15} = 2.3 \text{ pm/v}$
Effective Nonlinearity Expressions	$d_{\text{eff}}(l) = (d_{24} - d_{15}) \sin^2 f \sin^2 q - (d_{15} \sin^2 f + d_{24} \cos^2 f) \sin q$
Electro-optic Coefficients (Low frequency)	$r_{13} = 11.5 \text{ pm/V}$, $r_{23} = 15.4 \text{ pm/V}$, $r_{33} = 37.5 \text{ pm/V}$
Dielectric Constant	$\epsilon_{\text{eff}} = 42$

Specifications for finished KTA

Wavefront distortion: less than $\lambda/4$ @ 633 nm

Dimension tolerance: (W +/- 0.1 mm) x (H +/- 0.1 mm) x (L + 0.2 mm/-0.1mm)

Clear aperture: > 90% central area

Flatness: $\lambda/8$ @ 633 nm

Scratch/dig: 10/5 to MIL-O-13830A

Parallelism: better than 20 arc seconds

Perpendicularity: 5 arc minutes

Angle tolerance: $Dq < +/-0.25\sigma$, $Df < +/-0.25\sigma$

Coating and Mount

Standard dual band anti-reflection (DBAR) coatings at 1064nm/1530 nm, 1064/3200nm, or 1320nm/660nm are available. Other coatings are also available upon request. Mounts may be provided free of charge.

Ovens and Temperature Controllers

We provide ovens and precision temperature controllers to hold crystals and maintain them at a given temperature. Such a high temperature is often required for noncritical phase matching (NCPM) or to avoid optical damage of crystals.

Part Number: OVN6421

Power Consumption: 50W

AC Voltage : 110V (220/110V voltage converter will be provided for customers out side of North America)


Temperature Sensor: RTD Pt100

Operating Temperature Range: Room Temperature - 200°C

Temperature Stability: 0.1°C @148°C (Standard Deviation)

Host Crystal Dimension: 2x2x5mm to 7x7x20mm

Oven External Size: ϕ 50x55mm

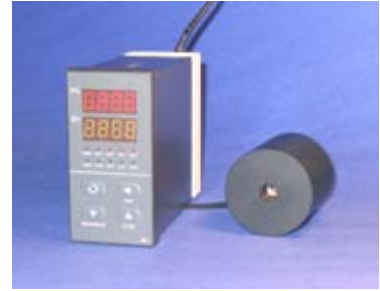

Crystals may be pre-mounted in the oven upon customer's request. Custom-made oven and temperature controller are also available for your specific applications. Specifications are subject to change without notice.

Application Examples:

Noncritical Phasematching

LBO: SHG of Nd:YAG/YLF/YVO4 lasers (148-170°C),

OPO pumped by SHG of Nd:YAG/YLF/YVO4 or Ti:Sapphire lasers (RT-200°C)

KNbO3: SHG of 860-950nm (y-cut) (20-180°C), SHG of 990-1064nm (z-cut) (20-188°C)

LiNbO3: SHG of Nd:YAG/YLF/YVO4 lasers (120°C)

KD*P: SHG of 532 nm (52.1 °C), ADP: SHG of 532 nm (51.2°C)

Reduction of optical damage

KTP, LiNbO3: Kept warm at 80°C

Protection from moisture

BBO, KD*P, KDP: Kept warm at well above the room temperature.